


PECORA-DECK 8013HB-VC PEDESTRIAN (Decorative Vinyl Chip, Standard Broadcast Option)

Application Instruction:

- A. Surface preparation.
- B. Prime concrete with Pecora P-801-VOC (<100g/L) or P-808 (<450g/L)¹ primer at 250 to 350 square feet per gallon.
- C. Apply base coat of Pecora 802 at 50 square feet per gallon (32 wet mils) OR 802 FC at 70 square feet per gallon (23 wet mils) using a ¼” notched squeegee. (Must apply base coat the same day as priming, otherwise reprime.)
- D. Allow 802 to cure 16-24 hours OR 802FC 4-6 hours. Base coat should be cured to a firm but tacky rubber at time of subsequent coating application.
- E. Apply top coat of Pecora HB1000 at 120 square feet per gallon (13 wet mils) using a ⅛” notched squeegee.
- F. While the Pecora HB1000 is still fluid, broadcast 16/35 mesh silica sand at 10-15 lbs./100 ft² and immediately backroll to encapsulate the aggregate.
- G. Again, while the Pecora HB1000 is still fluid, broadcast 2mm decorative vinyl chips at a rate of 2 lbs./100 ft² (as shown) and allow top coat to fully cure.

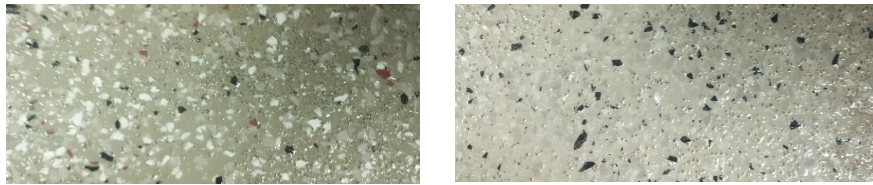

- H. Apply 806 Clear Top Coat at 80 square feet per gallon using a 3/16” notched squeegee and backroll with ½” nap roller for even coverage.
- I. Allow Top Coat to cure 24-48 hours prior to exposing to traffic.

HB1000 Decorative Vinyl Chip System	Components & Mil (Inch) Thickness, wet/dry									Total Mil (Inch) Thickness		Aggregate/s, Silica Sand, mesh (inch) Vinyl Chip, mm (Inch)
	Base Coat	Mil (Inch) Thickness		Top Coat	Mil (Inch) Thickness		Clear Top Coat	Mil (Inch) Thickness		WET	DRY	
		Wet	Dry		Wet	Dry		Wet	Dry			
Pedestrian	n/a	0	0	HB1000	13 (.013)	13 (.013)	806	20 (.013)	11 (.011)	33 (.013)	24 (.024)	16/35 (.047/.019) 2 (.047/.019)
	802FC	23 (.023)	23 (.023)	HB1000	13 (.013)	13 (.013)	806	20 (.013)	11 (.011)	56 (.036)	47 (.047)	16/35 (.047/.019) 2 (.047/.019)
	802	32 (.032)	26 (.026)	HB1000	13 (.013)	13 (.013)	806	20 (.013)	11 (.011)	65 (.045)	50 (.050)	16/35 (.047/.019) 2 (.047/.019)

CAUTION: Pecora-Deck Systems form a non-breathing membrane and therefore are generally not used on-grade or outside on concrete surfaces poured over vapor barriers (such as unvented metal decks or between slab membranes). Consult Pecora Technical Service for applications on-grade, over unvented metal decks or concrete with between slab membranes.

¹ Check local VOC regulations for product compliance prior to installing deck coating primer.

² Employees using crystalline silica must wear an approved respirator if the exposure is above the permissible exposure level. Consult manufacturer’s guidelines for safety practices.

